



AIMS & SCOPE

EDITORIAL  
BOARD

CALL FOR  
PAPER

SUBMIT AN  
ARTICLE

PAYMENT  
OPTION

FAQ

CONTACT US

# INDEXING

● OTHER SOURCE ●

IJERD is now being indexed with Index Copernicus, Google Scholar, Informatics, ProQuest, Research Gate, Docstoc, Scribd, UlrichWeb, Internet Archive Academia.edu, Computer Science Directory, Wepapers, Geond, Auburn University, Aalborg University, Queen's University, Goethe University

The Manuscript/paper can be submitted via email to [ijerd@editormails.com](mailto:ijerd@editormails.com)

## IJERD Menu

- ▶ Why publish with us
- ▶ Important Dates
- ▶ Indexing
- ▶ Hard Copy of IJERD
- ▶ Know Your Paper Status
- ▶ Subscription Alert
- ▶ Digital E-Certificate


## DOWNLOAD

- ▶ IJERD Paper Format
- ▶ Copy Right Form


## IJERD Contents

- ▶ Current Issue
- ▶ Archive

## IJERD Libraries



## Open Access

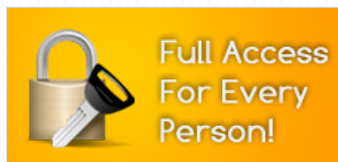

### IJERD : Indexing



**Academic Journals Database** is a universal index of periodical literature covering basic research from all fields of knowledge, and is particularly strong in medical research, humanities and social sciences. Academic Journals Database contains complete bibliographic citations, precise indexing, and informative abstracts for papers from a wide range of periodicals....

The objective of **J-STAGE** is to strive for acceleration and internationalization of science and technology information transmission and circulation by building on the Internet a uniform flow - from the submission to release of science and technology information....



**Cabell Publishing, Inc.**, was founded in 1978, our goal is to help professors, graduate students and researchers to publish their manuscripts in academic journals. To achieve this objective the company strives to maintain current contact information and websites for a large number of journals...

**Q-Sensei** pools and processes a vast amount of information from the Internet and makes it better accessible to its users with its patented Search and Presentation engine. Search results are displayed clearly and comprehensively while cross references with rich content enable the user to gain more insight and understand search.....



The aim of the **Directory of Open Access Journals** is to increase the visibility and ease of use of open access scientific and scholarly journals thereby promoting their increased usage and impact. The Directory aims to be comprehensive and cover all open access scientific and scholarly journals that use a quality control system to guarantee the content....

**Jour Informatics** is a non-profitable organization. It is a medium for introducing the Journals to the researchers. This service helps researchers to finding appropriate Journal for referencing and publishing their quality paper. In this global world, there are lots of Journals. So it is very difficult to find best relevant Journal which can be useful for us. ...



QR Code



ISO Certified



Microsoft Academic Search is a service developed by Microsoft Research to help scholars, scientists, students, and practitioners quickly and easily find academic content, researchers, institutions, and activities. Microsoft Academic Search indexes not only millions of academic papers.....

**Index Copernicus Journals** is a journal indexing, ranking and abstracting site. This service helps a journal to grow from a local level to a global one as well as providing complete web-based solution for small editorial teams. IC Journals helps to professionally manage your journal from your location and automatically delivers.....



**Computer science Directory**; we strive to provide the biggest authentic resource for computer sciences including computer science conferences, professionals, relevant publications, research institutes, organizations, computer science reference, and academic departments.....

**Ulrich's™** is the authoritative source of bibliographic and publisher information on more than 300,00 periodicals of all types academic and scholarly journals, Open Access publications, peer-reviewed titles, popular magazines, newspapers, newsletters and more from around the world. It covers all subjects, and includes publications.....



**EBSCO** offers many benefits to publisher partners. EBSCO is the only database aggregator that is also a subscription agent. As a result, the company has a unique understanding of the needs and concerns of publishers, and offers various ways for publishers to gain exposure for their publications and explore.....

**Scirus** is the most comprehensive scientific research tool on the web. With over 460 million scientific items indexed at last count, it allows researchers to search for not only journal content but also scientists' homepages, courseware, pre-print server material, patents and institutional repository and website information.....



**Google Scholar** provides a simple way to broadly search for scholarly literature. From one place, you can search across many disciplines and sources: articles, theses, books, abstracts and court opinions, from academic publishers, professional societies, online repositories, universities and other web sites.....

**ProQuest** connects people with vetted, reliable information. Key to serious research, the company has forged a 70-year reputation as a gateway to the world's knowledge – from dissertations to governmental and cultural archives to news, in all its forms. Its role is essential to libraries and other organizations.....



**Scientific Commons** is a project of the University of St. Gallen *Institute for Media and Communications Management*. The major aim of the project is to develop the world's largest archive of scientific knowledge with fulltexts freely accessible to the public.....

**CiteSeer<sup>x</sup>** is an evolving scientific literature digital library and search engine that focuses primarily on the literature in computer and information science. CiteSeerx aims to improve the dissemination of scientific literature and to provide improvements in functionality, usability, availability, cost, comprehensiveness.....



**Welcome to NewJour**, the New Journal and Newsletter Announcement List for new serials on the Internet. Information for subscribing, unsubscribing, and setting "digest" and "nomail" options appears below. NewJour aims to accomplish two objectives; it is both a list and a project....





AIMS & SCOPE

EDITORIAL  
BOARD

CALL FOR  
PAPER

SUBMIT AN  
ARTICLE

PAYMENT  
OPTION

FAQ

CONTACT US

ARCHIVE

OTHER SOURCE

IJERD is now being indexed with Index Copernicus, Google Scholar, Informatics, ProQuest, Research Gate, Docstoc, Scribd, UlrichWeb, Internet Archive Academia.edu, Computer Science Directory, Wepapers, Geond, Auburn University, Aalborg University, Queen's University, Goethe University

The Manuscript/paper can be submitted via email to [ijerd@editormails.com](mailto:ijerd@editormails.com)

IJERD Menu

- Why publish with us
- Important Dates
- Indexing
- Hard Copy Of Your Journal
- Know Your Paper Status
- Subscription Alert
- Digital E-Certificate

DOWNLOAD

- IJERD Paper Format
- Copy Right Form


IJERD Contents

- Current Issue
- Archive

IJERD Libraries



Open Access

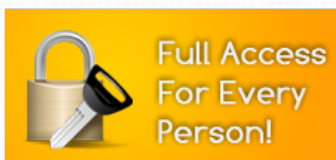

IJERD : Volume 12 - Issue 10

Version - 1 (October 2016)

**J. Renuka Kumari, K.V. Valsarajan**

**Reliability Based Design and Optimization of Trusses by Genetic Algorithms**

Abstract

Keywords


Reference

Full Article

Reliability is the probability that a structure will not fail to perform its intended function. Genetic Algorithms have been shown to be very effective optimization technique for number of engineering problems. In this paper reliability analysis of a ten bar truss and optimization by genetic algorithms is presented.


Reliability, Optimization, Reliability Based Design Optimization

- [1]. Charles Camp, Shahram Pezeshk and Guozhong Cao (1998). Optimized Design of Two Dimensional Structures Using A Genetic Algorithm. Journal of Structural Engineering, Vol. 124, No.5, 551-559.
- [2]. Chen, J.J and Duan, B.Y(1994) Structural Optimization by Displaying the Reliability Constraints. Computers and Structures, Vol. 50, No.6, 777-783.
- [3]. Ghasemi, M.R and Yousefi, M(2011) Reliability-Based Optimization of Steel Frame Structures Using Modified Genetic Algorithm. Asian Journal of Civil Engineering (Building And Housing), Vol. 12, No. 4 , 449-475.
- [4]. Goldberg, D. E.(1989), Genetic Algorithms in Search, Optimization, and Machine Learning. Reading, Massachusetts. Addison- Wesley Publishing Company.
- [5]. Hansofer , A.M. and Lind, N.C(1974), An Exact and Invariant First Order Reliability Format, Journal of Engineering Mechanics, ASCE, Vol.100, EM-1,111-121.

Citation	<b>J. Renuka Kumari, K.V. Valsarajan</b> "Reliability Based Design and Optimization of Trusses by Genetic Algorithms" published at <i>International Journal of Engineering Research and Development, Volume 12, Issue 10 (October 2016)</i>
MID	1210.067X.0001. India
Page	01-06
Download	 PDF

**Deepak Kumar, Prof. Rahul Shrivastava**

**Review on Fault Tolerant Reversible Arithmetic N-bit Adder/ Subtractor**

Citation	<b>Divesh Kumar, Amritpal Singh, Satish Kansal</b> "An Adaptive Approach to Positioning And Optimize Size of DG Source to Minimise Power Loss in Distribution Network" published at <i>International Journal of Engineering Research and Development</i> , Volume 12, Issue 10 (October 2016)
MID	1210.067X.0009. India
Page	52-57
Download	

**Elizabeth Refugio-García, Oscar F. Olea-Mejía, José G. Miranda-Hernández, Jessica J. Osorio Ramos, Enrique Rocha Range**

### Improving Toughness of Alumina-Based Composites to Be Used As Bone Substitute

Abstract

Keywords

Reference

Full Article

In this study it is show the experimental results of alumina reinforced with titanium additions, forming a composite which by its components could be classified as a biomaterial. The experimental results indicate that Al<sub>2</sub>O<sub>3</sub>-X wt. % Ti, (X = 0.5, 1, 2 and 3) composite material is an alternative material for its use as human bone substitute, because its density, porosity and toughness are better than of the human bone. Composites were manufactured using powders techniques. The results indicate that these composites have densities between 3.6 - 3.9 g/cm<sup>3</sup>, values far higher than the density of the compact bone of 1.8 g/cm<sup>3</sup>. The microstructure observed by scanning electron microscopy, shows a homogeneous distribution of titanium particles in the alumina matrix. Fracture toughness of the proposed composite present's values range between 3.3 to 8.76 MPam-0.5, whereas fracture toughness of compact bone has a value of 4.05-4.32 MPam-0.5

Alumina/titanium, Biomaterial, Alumina reinforced, Toughness, Bone

[1]. M. T. Angulo Carrere, D. Álvarez, *Biomecánica Clínica-Biomecánica de los Ligamentos*, Reduca (Enfermería, Fisioterapia y Podología) Serie Biomecánica Clínica, Madrid; 2010.

[2]. T. L. Norman, D. Vashisth, D. N. Burr, "Fracture Toughness of human bone under tension", *Journal of Biomechanics*, vol. 28, pp. 309-311, 1995.

[3]. J. Yan, K. B. Clifton, J. J. Mecholsky Jr., L. A. Grower, "Effect of the temperature on the fracture toughness of compact bone", *Journal of Biomechanics*, vol. 40, pp. 1641-1645, 2006.

[4]. J. Yan, A. Daga, R. Kumar, J. J. Melchosky Jr., "Fracture toughness and work of fracture of hydrated, dehydrated, and ashed bovine bone", *Journal of Biomechanics*, vol. 41, pp. 1929-1936, 2008.

[5]. R. B. Cook, P. Zioupos, "The fracture toughness of cancellous bone". *Journal of Biomechanics*. Vol. 42, pp. 2054-2060, 2009.

Citation	<b>Elizabeth Refugio-García, Oscar F. Olea-Mejía, José G. Miranda-Hernández, Jessica J. Osorio Ramos, Enrique Rocha Rangel</b> "Improving Toughness of Alumina-Based Composites to Be Used As Bone Substitute" published at <i>International Journal of Engineering Research and Development</i> , Volume 12, Issue 10 (October 2016)
MID	1210.067X.0010. México
Page	58-63
Download	

Version - 3 (October 2016)

**Hichem Trabelsi, Sabiha Sleimi, Noamen REBAI**

### Study of Morphometric And Hydrological Characteristics of Watersheds And Their Impact on The Silting of Small Lakes in the Tunisian Dorsal

Abstract

Keywords

Reference

Full Article

The siltation problem is a problem That Concerns Geomorphologists, hydrologists and Sedimentologists in terms of area dynamics. Indeed, control of silting reserves for Assessment Primarily to Comprehensively the importance of sediment transport. In Tunisia, the processes of erosion, transportation and deposition are Widespread and hold great importance in terms of national interest and in research as They Are Relatively difficulty to model and can cause damage Among --other cut. The objective of this study is to try to identify the morphological parameters of the watershed or river system HAVING the gold predominant role hand on the siltation of small lakes.....

Water erosion, Hill Lake, watershed runoff model, siltation, Tunisian dorsal.



## **Improving Toughness of Alumina-Based Composites to Be Used As Bone Substitute**

Elizabeth Refugio-García<sup>1,2</sup>, Oscar F. Olea-Mejía<sup>1</sup>, José G. Miranda-Hernández<sup>1</sup>  
Jessica J. Osorio Ramos<sup>2</sup> and Enrique Rocha Rangel<sup>3\*</sup>

<sup>1</sup>Universidad Autónoma Del Estado De México (UAEM-Valle De México), IIN, Blvd. Universitario S/N, Predio San Javier, Atizapán De Zaragoza, Edo. De México,

<sup>2</sup>Departamento De Materiales, Universidad Autónoma Metropolitana, Av. San Pablo 180, Col. Reynosa-Tamaulipas, México, D. F.,

<sup>3</sup>Universidad Politécnica De Victoria, Avenida Nuevas Tecnologías, Parque Científico Y Tecnológico De Tamaulipas, Cd. Victoria, Tamaulipas, México,

---

**Abstract:-** In this study it is show the experimental results of alumina reinforced with titanium additions, forming a composite which by its components could be classified as a biomaterial. The experimental results indicate that Al<sub>2</sub>O<sub>3</sub>-X wt. % Ti, (X = 0.5, 1, 2 and 3) composite material is an alternative material for its use as human bone substitute, because its density, porosity and toughness are better than of the human bone. Composites were manufactured using powders techniques. The results indicate that these composites have densities between 3.6 - 3.9 g/cm<sup>3</sup>, values far higher than the density of the compact bone of 1.8 g/cm<sup>3</sup>. The microstructure observed by scanning electron microscopy, shows a homogeneous distribution of titanium particles in the alumina matrix. Fracture toughness of the proposed composite present's values range between 3.3 to 8.76 MPam<sup>-0.5</sup>, whereas fracture toughness of compact bone has a value of 4.05-4.32 MPam<sup>-0.5</sup>.

**Keywords:-** Alumina/titanium, Biomaterial, Alumina reinforced, Toughness, Bone

---

### **I. INTRODUCTION**

Human bones are composed of organic materials, minerals, and water; These bones are not entirely solid but have small spaces into its components, forming small channels through which the blood vessels circulating nutrient exchange charge, depending on the size of these pores can be of compact bone type (also called cortical) or spongy or trabecular bone<sup>1</sup>. Much research has focused on the characterization of different types of bones bovine, canine equine animals or human, and turn recent research has focused on finding materials that may have properties similar to human bones[1-5].

Recently, they had been significant progress in improving the ability of ceramic materials for use in structural applications. In particular their resistance has improved dramatically, to the point that today some ceramics can compete with metals in certain applications that previously would have been unimaginable their use[6].

However, regarding the mechanical properties of fracture toughness of ceramic materials still today continues making arduous research for improve it, because they are very fragile, according to recent studies ceramic materials can be toughened by incorporating fine particles of metal in its matrix, this development has been successfully used in different systems[7]. Some of these studies are focused on the strengthening mechanisms, in where it is possible to indicate that the size of the nonmetallic inclusion and homogeneous distribution thereof in the ceramic matrix is very important to ensure obtaining a composite material having good toughness[8].

Biocomposites using ceramic matrix are generally manufactured of alumina-ZrO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub> or hydroxyapatite (HAp)[9] that when are reinforced with polymers or metals it is achieved to reduce the elastic modulus of the composite material making it closer to the real bone, which lowers the stresses generated at the junctions of the implant with the bone. However, the main processes by which these composites are manufactured is extrusion, generating composites which present low values of toughness, reliability and mechanical strength, causing tribological abnormalities, originating surface wear of the biocomposites and sometimes the final break of the material. So that the fracture toughness, strength and wear are important factors which restrict their possible application as a biomaterial for use as prosthetics, therefore it must generate new composite materials whose processing routes let to improve these properties.

One such ceramic regarded as suitable candidates for making composite materials is alumina (Al<sub>2</sub>O<sub>3</sub>) which is a material having a high resistance to abrasion factors in both low and high temperatures and good

wear resistance in corrosive environments, besides that alumina is a ceramic having good biocompatibility with the body and may be feasible to use it as a substitute for bone in the human body because of this feature.


## II. EXPERIMENTAL

Composites were fabricated using two materials as raw materials classified as natural biomaterials, alumina (Sigma Aldrich, 99.9% purity, 100 nm-100  $\mu\text{m}$ ) and titanium (Aldrich, 99.99% purity, 5-10  $\mu\text{m}$ ). These materials were used in the preparation of binary mixtures of composition  $\text{Al}_2\text{O}_3\text{-X wt. \% Ti}$ , (X = 0.5, 1, 2 and 3). The mixtures were subjected to intense grinding at 300 rpm for 3h with spherical grinding media 13 mm, using  $\text{ZrO}_2$  grinding ratio 1:20. The powder mixture was then compacted by uniaxial cold pressing at 350MPa in order to form cylindrical pellets, 1 cm in diameter and 0.3 cm height. The obtained compacts were sintered in an electric furnace with MoSi2 heating elements at temperatures of 1400 °C for 1, 2 and 3 hours in a nitrogen atmosphere. Physical characterization was done by determining the density and porosity by the method of Archimedes; the mechanical properties of hardness and fracture toughness were determined using the method of indentation from measurements of the lengths of the cracks generated in the Vickers indentation with a Emco Durometer Test[10]. Finally, composites were prepared by ceramograph techniques to be observed by scanning electron microscopy. The values of density, hardness and fracture toughness will be compared with the same properties of human compact bones.

## III. RESULTS AND DISCUSSION

### A. Density and porosity

The density of the  $\text{Al}_2\text{O}_3\text{-Ti}$  composites was determined after performing sintering treatment at 1400 °C during 1, 2 and 3 hours, the obtained values are between 3.6-3.9  $\text{g/cm}^3$ , which are within the theoretical density values 3.83-3.90  $\text{g/cm}^3$  determined by the rule of mixtures, considering 3.95  $\text{g/cm}^3$  as the density of the alumina and 4.51  $\text{g/cm}^3$  as the density of titanium; results density of alumina based composites exceed by more than 200% of the density of human compact bone (1.8  $\text{g/cm}^3$ ). The porosity of the alumina based composites is shown in Fig. 1, the graphs show the percentage of porosity in composites as a function of the titanium content and of sintering treatment time, in this way porosity is lower when the titanium content is greater, on the other hand, products with lower porosity are obtained when the sintering treatment is longer (3 hours). It is important to emphasize the effect in decreasing porosity (sample's densification) due to titanium presence, situation due to the good thermal conductivity of titanium that promotes diffusion mechanisms during sintering.

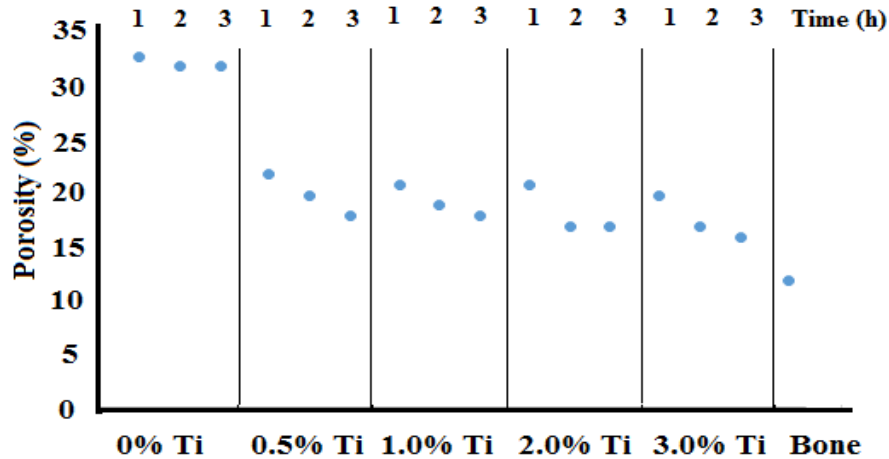

**Fig. 1:** Porosity of composites  $\text{Al}_2\text{O}_3\text{-X wt. \% Ti}$ , (X = 0.5, 1, 2 and 3), and porosity of human compact bone

### B. Fracture toughness

The fracture toughness is shown in Fig. 2. in all cases it is observed that the presence of titanium in the alumina improves the fracture toughness of the composite, more even when titanium contents are above 2% by weight. Comparing the fracture toughness of the samples with 3% titanium sintered for 2 and 3 hours at 1400 °C, it has which reaches 32% highest values compared with the value of the tenacity of human bone. So that the titanium effectively acts as a means of strengthening alumina, some researches[11-13] have suggested that the mechanism, by which metals reinforced alumina, is the cracks deflection due to the presence of a ductile metal in the ceramic matrix.

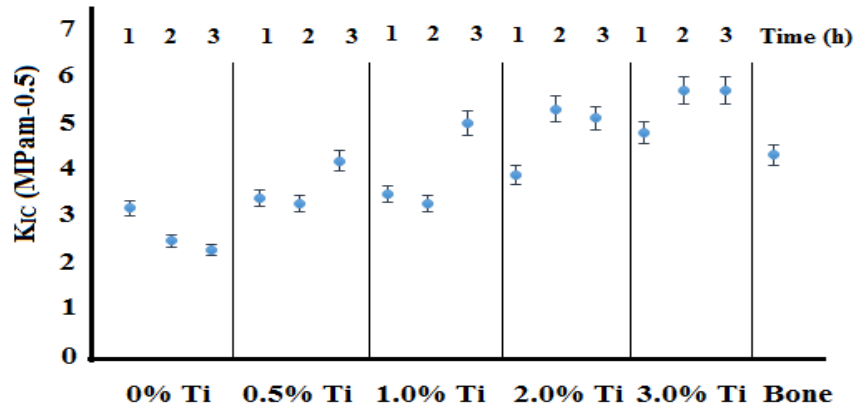


Fig. 2: Fracture toughness of composites Al<sub>2</sub>O<sub>3</sub>-X wt. % Ti, (X = 0.5, 1, 2 and 3), and fracture toughness of human compact bone

### C. Hardness

In Fig. 3. the hardness values are observed according to both the amount of titanium in the composite and sintering treatment time. Comparing hardness of 350 HV in compact bone with the hardness obtained in the Al<sub>2</sub>O<sub>3</sub> composites, it can be seen that all manufactured composites present hardness values exceeding those of compact bone, this situation is logical because the alumina is an extremely hard material that when mixed with a more ductile metal reduces its hardness. Hence the composite hardness values tend to be more similar to those of alumina in the way as the titanium content increases by this.


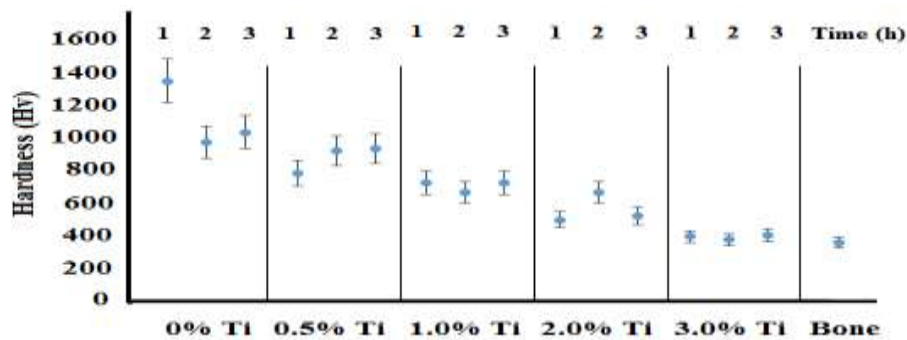


Fig. 3: Hardness of composites Al<sub>2</sub>O<sub>3</sub>-X wt. % Ti, (X = 0.5, 1, 2 and 3), and hardness of human compact bone


### D. MICROSTRUCTURE

Fig. 4. shows micrographs obtained by scanning electron microscopy in Al<sub>2</sub>O<sub>3</sub>-X wt. % Ti, (X = 0.5, 1, 2 and 3) composites, sintered at 1400 °C during 2 hours. In all samples are observed microstructures with irregularly grains, having average sizes ranging from 1 micron to little less than 10 microns, in some very large grains they are observed due to abnormal grain growth, this is seen more at higher sintering times, situation which is logical because large sintering times allow greater diffusion of atoms between grains. For the control sample (0% Ti) a partially sintered microstructure is observed, it means sintering conditions, principally the temperature of 1400°C, It was not high enough to achieve good densification of the ceramic, and greater activation energy is here required to consolidate the body. When the microstructures with additions of titanium in all studied percentages, it is observed a different situation, since in these samples it can be seen better consolidated bodies, situation further improved with increases in sintering times and titanium % in the matrix. This can be explained by the fact that having a metal present as titanium, which it is a good conductor of heat, the diffusion mechanism are favored between the particles that make up the material, situation that is not necessary to increase the temperature to achieve better consolidated bodies, as it would be necessary in a pure ceramic as is the case of alumina. Although, in the samples it is observed grain growth as a function of sintering time, this is minimum. It is also possible to observe that titanium is in the form of very fine particles of lighter color than the matrix, which would presumably be in this position will block the growth of cracks when they try to pass where lies this. Likewise, no significant presence of porosity it is observed in the microstructure. With respect to the microstructure of human bone, it has which is much thinner compared to the composites produced here.

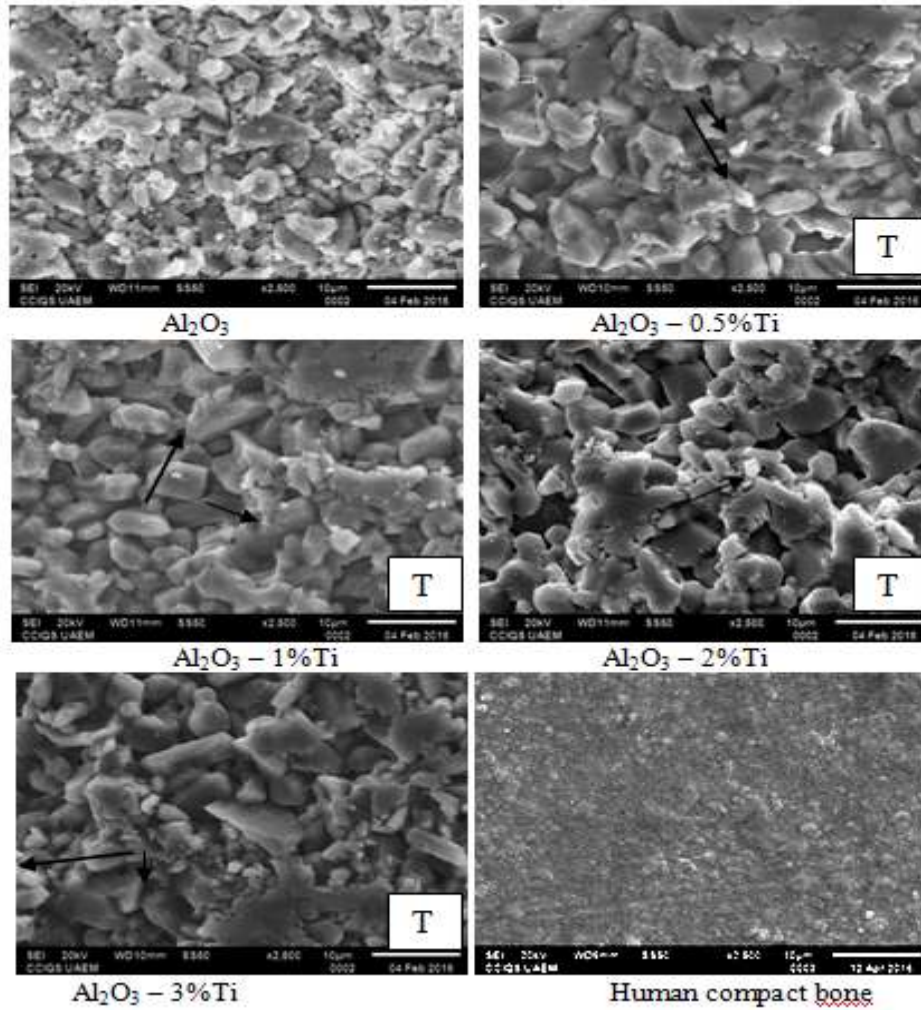

**Fig. 4:** Microstructure of composites  $\text{Al}_2\text{O}_3$ -X wt. % Ti, (X = 0.5, 1, 2 and 3), sintered at  $1400^\circ\text{C}$  during 2h, and microstructure of human compact bone


Fig. 5. shows typical results of microanalysis performed with X-rays energy dispersive (EDX) executed in samples with 0% and 3 wt. % Ti in a punctual manner in the clear and dark particles of the microstructure. For the case of the sample with 0 wt. % Ti, obtained spectra indicate the presence of oxygen and aluminum in the sample, feature that corresponds to the composition of the ceramic matrix ( $\text{Al}_2\text{O}_3$ ). In the case of the sample with 3 wt. % Ti of SEM photomicrographs shown in Figure 4, the presence of two phases is observed, in accordance with the EDX spectra. The darkest phase corresponds to the ceramic matrix, whereas the clearest phase corresponds to the Ti present in the sample. Thus, it can be seen that Ti particles are located in intergranular positions and also have a much smaller size compared with the  $\text{Al}_2\text{O}_3$  grains.

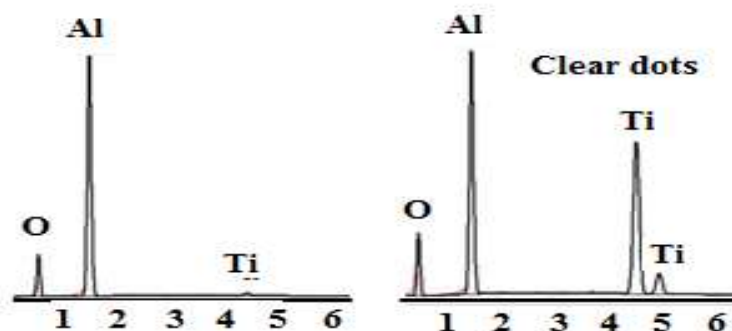

**Fig. 5:** EDX spectra corresponding to  $\text{Al}_2\text{O}_3$ /0.0 wt % Ti and  $\text{Al}_2\text{O}_3$ /3 wt % Ti sintered at  $1400^\circ\text{C}$  for 2 hours




In Fig. 6. It is observed and indentation obtained during microhardness testing of samples with 3 wt. % Ti sintered for 3 hours at 1400°C. In this figure, it can be seen that the crack generated at the apex of the mark spreads and stops when it encounters a particle of Ti, so that it may be concluded that in the Al<sub>2</sub>O<sub>3</sub>-Ti system when a crack grows and hits a particle of Ti, the ductility and plastic deformation of the metal inhibits the growth of the crack or promotes its search for another propagation path, causing a higher demand of energy for the crack to grow, resulting in an increase in fracture toughness of the material, explaining in this case the strengthening of Al<sub>2</sub>O<sub>3</sub> by means of Ti..

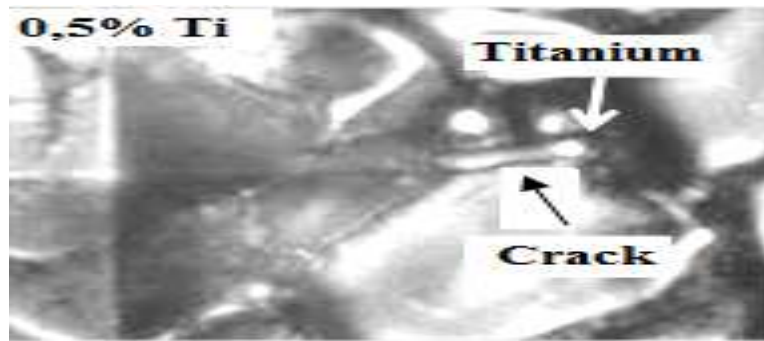

**Fig. 6:** Crack generated at the apex of the indentation mark during microhardness testing in sample with 3 wt. % Ti sintered for 3 hours at 1400°C

In Fig. 7: It is presented the fracture surface of samples with 3 wt. % Ti sintered for 3 hours at 1400°C. In this figure a way brittle fracture is observed, it can be seen well detachment alumina grains from each other, without any deformation in the same, also it is seen that titanium particles are located at the grain boundaries which were also torn during fracture of the material.

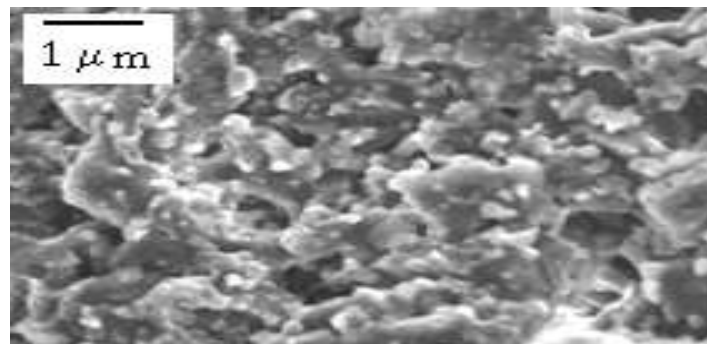

**Fig. 7:** Fracture surface in an Al<sub>2</sub>O<sub>3</sub>/Ti reinforced composite

#### IV. CONCLUSIONS

- Through proposed methodology it is possible to manufacture alumina based composites with improved values of fracture toughness, making possible its use in biomedical applications.
- The composites Al<sub>2</sub>O<sub>3</sub>-X wt. % Ti, (X = 0.5, 1, 2 and 3), can be classified as biomaterials, because the raw material with which these composites are manufactured are considered natural biomaterials.
- The Al<sub>2</sub>O<sub>3</sub> composite containing 2 or 3 wt. % titanium and that was sintered at 1400 °C during 2 hours, exhibits values exceeding 32 % fracture toughness of a human compact bone.
- All manufactured composites of the Al<sub>2</sub>O<sub>3</sub>-X wt. % Ti, (X = 0.5, 1, 2 and 3) present hardness values exceeding those of compact bone.

#### ACKNOWLEDGMENT

Financial and technical support from the UAM-A are gratefully acknowledged.

#### REFERENCES

- [1]. M. T. Angulo Carrere, D. Álvarez, *Biomecánica Clínica-Biomecánica de los Ligamentos*, Reduca (Enfermería, Fisioterapia y Podología) Serie Biomecánica Clínica, Madrid; 2010.
- [2]. T. L. Norman, D. Vashisth, D. N. Burr, "Fracture Toughness of human bone under tension", *Journal of Biomechanics*, vol. 28, pp. 309-311, 1995.

- [3]. J. Yan, K. B. Clifton, J. J. Mecholsky Jr., L. A. Grower, "Effect of the temperature on the fracture toughness of compact bone", *Journal of Biomechanics*, vol. 40, pp. 1641-1645, 2006.
- [4]. J. Yan, A. Daga, R. Kumar, J. J. Melchosky Jr., "Fracture toughness and work of fracture of hydrated, dehydrated, and ashed bovine bone", *Journal of Biomechanics*, vol. 41, pp. 1929-1936, 2008.
- [5]. R. B. Cook, P. Zioupos, "The fracture toughness of cancellous bone". *Journal of Biomechanics*. Vol. 42, pp. 2054-2060, 2009.
- [6]. Y. Miyamoto, W. A. Kaysser, B. H. Rabin, A. Kawasaki, R. G. Ford eds. *Functionally Graded Materials; Design, Processing and Applications*, Kluwer Academic, USA; 1999.
- [7]. O. L. Ighodaro, O. I. Okoli, "Fracture Toughness Enhancement for Alumina Systems: A review", *International Journal of Applied Ceramic Technology*. Vol. 5, pp 3-15, 2008.
- [8]. L. Mas Gutiérrez, A. Altamirano Torres, F. Sandoval Pérez, E. Rocha Rangel, "Alumina Matriz Composites with Aluminide Phases", *Proceedings 5th International Conference on High-Temperature Ceramic Matrix Composites – HTCMC5*, Seattle, USA. Sept. 12-16, 2004.
- [9]. T. R. Hernández, C. R. Palma, M. B. Piña, "Hidroxiapatita y sus Aplicaciones", *Physics Mexican Journal*, vol. 45, pp. 1144-1147, 1999.
- [10]. A. G. Evans, E. A. Charles, "Fracture Toughness Determination by Indentation", *Journal of American Ceramic Society*, vol. 59, pp. 371-372, 1976.
- [11]. N. Travirskya, I. Gotmanb, N. Claussen, "Alumina–Ti aluminide interpenetrating composites: microstructure and mechanical properties", *Materials Letters*, vol. 57, pp. 3422-3426, 2003.
- [12]. C. Marci, P. Katarzyna, "Processing, microstructure and mechanical properties of Al<sub>2</sub>O<sub>3</sub>–Cr nanocomposites", *Journal of European Ceramic Society*, vol. 27, pp. 1273-1279, 2007.
- [13]. J. Lalande, S. Scheppokat, R. Jansen, N. Claussen, "Toughening of alumina/zirconia ceramic composites with silver particles", *Journal of European Ceramic Society*, vol. 22, pp. 2165-2168, 2002.